



UNIVERSITI PUTRA MALAYSIA

**PHOTODEGRADATION OF DYES
USING TITANIUM DIOXIDE SUPPORTED ON GLASS**

LEE KONG HUI

FSAS 2002 45

**PHOTODEGRADATION OF DYES
USING TITANIUM DIOXIDE SUPPORTED ON GLASS**

LEE KONG HUI

**MASTER OF SCIENCE
UNIVERSITI PUTRA MALAYSIA**

2002



**PHOTODEGRADATION OF DYES
USING TITANIUM DIOXIDE SUPPORTED ON GLASS**

By

LEE KONG HUI

**Thesis Submitted to the School of Graduate Studies, Universiti Putra Malaysia,
in Fulfilment of the Requirements for the degree of Master of Science**

July 2002



DEDICATION

I would like to dedicate my work to both my beloved parents for their full support to carry out my Master Degree Study in Universiti Putra Malaysia.

Abstract of thesis presented to the Senate of Universiti Putra Malaysia in fulfilment of the requirements for the degree of Master of Science

**PHOTODEGRADATION OF DYES
USING TITANIUM DIOXIDE SUPPORTED ON GLASS**

By

LEE KONG HUI

July 2002

Chairman : Associate Professor Zulkarnain Zainal, Ph.D

Faculty : Science and Environmental Studies

Photodegradation of dyes, in aqueous solution was carried out using titanium dioxide coated on glass plates, illuminated by blue fluorescent lamps. TiO₂ coated glass was prepared by sol-gel technique. Air was pumped into the mixture to ensure continuous supply of oxygen in the mixture.

Methylene blue removal was studied based on the effect of amount of coated TiO₂ sol-gel, initial concentration, light intensity, light source, and pH of solution medium. Comparison was also made to the powder form of TiO₂ which was prepared by the same method. The highest percentage of methylene blue removal was obtained when the photodegradation experiment was run using 5 pieces of TiO₂/Glass (4 times of sol-gel dip-coating) and 10 ppm of methylene blue solution at 28 °C after illumination under 4 white fluorescent lamps of 20 W for 4 hours. About 84 % of methylene blue was removed. Methylene blue removal was found to be efficient and comparable to the illumination using near UV light, sunlight, 4 white fluorescent lamps, 4 dark fluorescent lamps and 4 blue fluorescent lamps.

The best set of parameters for photodegradation process, such as the photocatalyst loading, initial concentration, light intensity, light source, and solution pH condition was determined. These parameters were used for the photodegradation process of methyl orange, chicago sky blue 6B, indigo carmine, mixed dyes (consist of methylene blue, methyl orange, chicago sky blue 6B, and indigo carmine), and industrial waste solution. Intermediates formed in the reaction pathway during photomineralization of methylene blue, methyl orange, indigo carmine, chicago sky blue 6B, mixed dyes, and industrial waste solution were analysed using High Performance Liquid Chromatography (HPLC) and Total Organic Carbon (TOC) analysers.

Abstrak tesis yang dikemukakan kepada Senat Universiti Putra Malaysia
sebagai memenuhi keperluan untuk ijazah Master Sains

**FOTODEGRADASI PEWARNA-PEWARNA MENGGUNAKAN KACA
TERDOKONG TITANIUM DIOKSIDA**

Oleh

LEE KONG HUI

Julai 2002

Pengerusi : Profesor Madya Zulkarnain Zainal, Ph.D.

Fakulti : Sains dan Pengajian Alam Sekitar

Fotodegradasi pewarna dalam larutan akueus telah dikaji dengan menggunakan kaca terdokong TiO_2 (TiO_2 /kaca) di bawah penyinaran lampu berpendaflor biru. Kaca terdokong TiO_2 disediakan dengan teknik sol-gel. Udara dipamkan masuk secara berterusan ke dalam larutan campuran untuk memastikan pembekalan gas oksigen yang secukupnya secara berterusan.

Kadar penyingkiran metilena biru telah dikaji berdasarkan kesan jumlah sol-gel TiO_2 yang telah didokongkan (kuantiti kaca yang telah digunakan), kepekatan awal, keamatan cahaya, sumber cahaya, dan keasidan medium larutan. Perbandingan juga dibuat terhadap penggunaan TiO_2 dalam bentuk serbuk. 5 keping TiO_2 /kaca didapati memberikan kadar penyingkiran metilena biru paling tinggi. Lebih kurang 84 % daripada larutan berkepekatan 10 ppm telah disingkirkan pada suhu 28 °C apabila disinari oleh 4 lampu berpendaflor putih berkuasa 20 W selama 4 jam. Dapat diketahui juga bahawa kadar penyingkiran metilena biru adalah berkesan dan setanding untuk penyinaran dengan menggunakan cahaya dekat UV, cahaya matahari, 4 lampu berpendaflor putih, 4 lampu berpendaflor gelap, dan 4 lampu berpendaflor biru.

Satu set parameter terbaik untuk proses fotodegradasi telah ditentukan. Ia telah digunakan untuk proses fotodegradasi metil oren, indigo karmina, chicago ski biru 6B, pewarna campuran (terdiri daripada metilena biru, metil oren, indigo karmina, dan chicago ski biru 6B), dan larutan sisa organik kilang. Bahan perantaraan yang terbentuk dalam proses tindak balas semasa fotomineralisasi metilena biru, metil oren, indigo karmina, chicago ski biru 6B, pewarna campuran, dan air buangan kilang telah dianalisis dengan menggunakan penganalisis Kromatografi Cecair Prestasi Tinggi (HPLC) dan Jumlah Karbon Organik (TOC).

ACKNOWLEDGEMENTS

Firstly, I wish to express my sincere thank to Associate Prof. Dr. Zulkarnain Zainal, Associate Prof. Dr. Mohd. Zobir Hussein, Associate Prof. Dr. Taufiq Yap Yun Hin and Dr. Irmawati Ramli for their invaluable assistance, advice, and guidance throughout the duration of the project.

I appreciate the guidance by the staffs, both in the Chemistry Department and Institute of Bioscience. In addition, I would also like to thank Mr. Osman Bin Jamaludin and Mr. Mohd. Zulhizan Bin Zakaria from Graduate Studies Institute, Universiti Malaya for helping me to run TOC analysis on my samples.

Thanks are due to my coursemates, Mr. Looi Ming Hoong, Mr. Rodhyrolin Shahadan, Mr. Goh Chee Keong, Mr. Tan Kian Peng, Mr. Leong Loong Kong, Mr. Fu Wooi Cheat, Ms. Ita Jong, laboratory members and to all who had contributed in this project.

Finally, financial support from IRPA funding (09-02-04-0104) is gratefully acknowledged.

I certify that an Examination Committee met on 31st July 2002 to conduct the final examination of Lee Kong Hui on his Master of Science thesis entitled "Photodegradation of Dyes Using Titanium Dioxide Supported on Glass" in accordance with Universiti Pertanian Malaysia (Higher Degree) Act 1980 and Universiti Pertanian Malaysia (Higher Degree) Regulations 1981. The Committee recommends that the candidate be awarded the relevant degree. Members of the Examination Committee are as follows:

ABD. HALIM ABDULLAH, Ph.D.,
Faculty of Science and Environmental Studies
Universiti Putra Malaysia
(Chairman)

ZULKARNAIN ZAINAL, Ph.D.,
Associate Professor,
Faculty of Science and Environmental Studies
Universiti Putra Malaysia
(Member)

MOHD. ZOBIR HUSSEIN, Ph.D.,
Associate Professor,
Faculty of Science and Environmental Studies,
Universiti Putra Malaysia.
(Member)

TAUFIQ YAP YUN HIN, Ph.D., CChem., MRSC,
Associate Professor,
Faculty of Science and Environmental Studies,
Universiti Putra Malaysia.
(Member)

IRMAWATI RAMLI, Ph.D.,
Lecturer,
Faculty of Science and Environmental Studies,
Universiti Putra Malaysia.
(Member)



SHAMSHER MOHAMAD RAMADILI, Ph.D.,
Professor/Deputy Dean
School of Graduate Studies,
Universiti Putra Malaysia

Date: 08 OCT 2002

This thesis submitted to the Senate of Universiti Putra Malaysia has been accepted as partial fulfilment of the requirements for the degree of Master of Science. The members of the Supervisory Committee are as follows.

ZULKARNAIN ZAINAL, Ph.D.,
Associate Professor,
Faculty of Science and Environmental Studies
Universiti Putra Malaysia
(Chairman)

MOHD. ZOBIR HUSSEIN, Ph.D.,
Associate Professor,
Faculty of Science and Environmental Studies,
Universiti Putra Malaysia.
(Member)

TAUFIQ YAP YUN HIN, Ph.D., CChem., MRSC,
Associate Professor,
Faculty of Science and Environmental Studies,
Universiti Putra Malaysia.
(Member)

IRMAWATI RAMLI, Ph.D.,
Lecturer,
Faculty of Science and Environmental Studies,
Universiti Putra Malaysia.
(Member)

AINI IDERIS, Ph.D.,
Professor/Dean
School of Graduate Studies,
Universiti Putra Malaysia

Date:

DECLARATION

I hereby declare that the thesis is based on my original work except for quotations and citations which have been duly acknowledged. I also declare that it has not been previously or concurrently submitted for any other degree at UPM or other institutions.



LEE KONG HUI

Date : 26 - 9 - 2002 .

TABLE OF CONTENTS

	Page
DEDICATION	ii
ABSTRACT	iii
ABSTRAK	v
ACKNOWLEDGEMENTS	vii
APPROVAL SHEETS	viii
DECLARATION FORM	x
TABLE OF CONTENTS	xi
LIST OF TABLES	xiii
LIST OF FIGURES	xv
LIST OF ABBREVIATIONS	xviii

CHAPTER

1	INTRODUCTION	1
	1.1 Theory of Semiconductor	3
	1.2 Properties of Titanium Dioxide	6
	1.2.1 Structural Properties	6
	1.2.2 Optical Properties	10
	1.2.3 Electrical Properties	12
	1.3 Photodegradation on Semiconductor	13
	1.4 Role of Oxygen	16
	1.5 Glass as Support for Titanium Dioxide (Glass/TiO ₂)	18
	1.6 Properties of Dyes	19
	1.7 Literature Review	25
	1.8 Objectives	30
2	METHODOLOGY	31
	2.1 Preparation of Titanium Dioxide Sol-Gel	31
	2.2 Preparation of Titanium Dioxide TiO ₂ Coated on Glass (TiO ₂ /Glass)	31
	2.3 Preparation of Dyes Solution	32
	2.4 Determination of Wavelength at Maximum Absorption (λ_{max}) and Construction of Standard Calibration Curve for Dyes	33
	2.5 Photodegradation of Methylene Blue	34
	2.5.1 Effect of Amount of TiO ₂ (Sol-Gel Dip-Coating Repetition)	34
	2.5.2 Effect of Initial Concentration	37
	2.5.3 Effect of Light Intensity	38
	2.5.4 Effect of Using Different Light Source	38
	2.5.5 Effect of Solution pH Condition	39
	2.5.6 TiO ₂ Powder of Dried Sol-Gel	39
	2.6 Photodegradation of Various Type of Dyes	40
	2.7 Photodegradation of Mixed Dyes	41
	2.8 Photodegradation of Industrial Waste Solution	42
	2.9 TiO ₂ /Glass Characterization	43



2.9.1 SEM-EDX Analysis	43
2.9.2 XRD Analysis	44
2.10 Fourier Transform-Infra Red (FT-IR) Analysis	45
2.11 Total Organic Carbon (TOC) Analysis	45
2.12 High Performance Liquid Chromatography (HPLC) Analysis	47
 3 RESULTS AND DISCUSSION	 48
3.1 Preparation of TiO ₂ /Glass	48
3.2 Surface Morphology and Composition of Dried TiO ₂ Sol-Gel	50
3.3 Surface Morphology of TiO ₂ . Coated on Glass (TiO ₂ /Glass)	53
3.4 XRD Characterization of TiO ₂ Compound	57
3.5 Infra Red (IR) Analysis for TiO ₂ Compound	62
3.6 Preliminary Tests	64
3.7 Effect of Amount of TiO ₂ (Number of Sol-Gel Dip-Coating)	69
3.8 Effect of initial Concentration	72
3.8.1 First Kinetics Order for Photodegradation Process	73
3.8.2 Pseudo-Second Kinetics Order for Photodegradation Process	77
3.9 Effect of Light Intensity	83
3.10 Effect of Different Light Source	84
3.11 Effect of Solution pH	89
3.12 TiO ₂ in Powder Form (Dried TiO ₂ Sol-Gel)	92
3.13 Photodegradation of Various Type of Dyes	96
3.14 Total Organic Carbon (TOC) Analysis	99
3.14.1 TOC Analysis for Methylene Blue	99
3.14.2 TOC Analysis for Methyl Orange	103
3.14.3 TOC Analysis for Chicago Sky Blue 6B	109
3.14.4 TOC Analysis for Indigo Carmine	111
3.14.5 TOC Analysis for Mixed Dyes	113
3.14.6 TOC Analysis for Industrial Waste Water Solution	117
3.15 High Performance Liquid Chromatography (HPLC) Analysis	120
3.15.1 HPLC Analysis for Methylene Blue	120
3.15.2 HPLC Analysis for Methyl Orange	121
3.15.3 HPLC Analysis for Indigo Carmine	122
3.15.4 HPLC Analysis for Chicago Sky Blue 6B	123
3.15.5 HPLC Analysis for Mixed Dyes (10 ppm)	124
3.15.6 HPLC Analysis for Mixed Dyes (2.5 ppm)	125
3.15.7 HPLC Analysis for Waste Water Solution	127
 4 CONCLUSION AND RECOMMENDATION	 128
4.1 Conclusion	128
4.2 Recommendation	131
 BIBLIOGRAPHY	 133
 APPENDICES	 136
 BIODATA OF THE AUTHOR	 154

LIST OF TABLES

Table	Page
1.1 Crystallographic properties of anatase, rutile and brookite (Shriver <i>et al.</i> ,7 1990)	
1.2 Properties of Methylene Blue	21
1.3 Properties of Methyl Orange	22
1.4 Properties of Indigo Carmine	23
1.5 Properties of Chicago Sky Blue 6B.....	24
3.1 Amount of TiO ₂ coated on the glass with different times of dip-coating.....	48
3.2 Standard deviation value and mean amount of TiO ₂ coated on the glass... ..	49
with different times of dip-coating	
3.3 Weight % and atomic % of the elements exist in dried TiO ₂	53
3.4 Element exist in the different coating area for 8 times of dip-coating	56
(atomic percent)	
3.5 Comparison of d (Å) values for all of the peaks exist in TiO ₂ /Glass with	58
different heating temperature	
3.6 Comparison of d (Å) values for all of the peaks exist in dried TiO ₂ powder	59
with TiO ₂ /Glass (100°C, 5 dip-coating)	
3.7 Effect of photocatalyst and light illumination on photodegradation process	65
of methylene blue	
3.8 Effect of photocatalyst and light illumination on photodegradation process	66
of methyl orange	
3.9 Effect of photocatalyst and light illumination on photodegradation process	67
of indigo carmine	
3.10 Effect of photocatalyst and light illumination on photodegradation process	68
of chicago sky blue 6B	
3.11 Percentage for total removal of methylene blue.....	69
3.12 Percentage for total removal of methylene blue with different initial	72
concentration	
3.13 The apparent rate constant, k_{app} , half time, $t_{1/2}$ and correlation factor, R_2	76
values for the photodegradation of methylene blue with different initial	
concentration	
3.14 The apparent rate constant, k_{app} and removal efficiency for the	79
photodegradation of methylene blue with different initial concentration	
3.15 The apparent rate constant, k_{app} and half time, $t_{1/2}$ for the.....	83
photodegradation of methylene blue with different light intensity	
3.16 Percentage for total removal of methylene blue with different light intensity.....	83
3.17 The apparent rate constant, k_{app} and half time, $t_{1/2}$ for the.....	87
photodegradation of methylene blue with different light source	
3.18 Percentage for total removal of methylene blue with different light source.....	87
3.19 The apparent rate constant, k_{app} and half time, $t_{1/2}$ for the.....	91
photodegradation of methylene blue with different pH condition	
3.20 Percentage for total removal of methylene blue with different pH condition.....	91
3.21 Percentage for total removal of methylene blue with different mass of dried	93
TiO ₂ powder	
3.22 The apparent rate constant, k_{app} and half time, $t_{1/2}$ for the.....	94
photodegradation of methylene blue with different mass of dried TiO ₂ powder	
3.23 Percentage for total removal of various dyes.....	98



3.24	The apparent rate constant, k_{app} and half time, $t_{1/2}$ for the.....	98
	photodegradation of various dyes.	
3.25	Total organic carbon contents of methylene blue	100
3.26	Total organic carbon contents of methyl orange	103
3.27	Total organic carbon contents of chicago sky blue 6B	109
3.28	Total organic carbon contents of indigo carmine	112
3.29	Total organic carbon contents of mixed dyes (initial concentration	114
	10 ppm).	
3.30	Total organic carbon contents of waste water solution.....	118

LIST OF FIGURES

Figure	Page
1.1 The energy diagram for a semiconductor, showing the band gap energy.....4 (Nogueira and Wilson, 1993).	4
1.2 Change in the electronic structure of a semiconductor compound as the5 number N of monomeric units present increase from unity to clusters of more than 2000 (Mills and Hunte, 1997).	5
1.3 Structure of anatase TiO ₂ , titanium dark, oxygen light (Shriver <i>et al.</i> , 1990).....8	8
1.4 Structure of rutile TiO ₂ , titanium dark, oxygen light (Shriver <i>et al.</i> , 1990).....9	9
1.5 Formation of surface hydroxyls (OH) on the anatase TiO ₂ surface.....10 a) An uncovered surface. b) Coordination of Ti ⁴⁺ ions by water molecules. c) The formation of surface hydroxyl ions by proton transfer from water to O ₂ ⁻ ions. (Shriver <i>et al.</i> , 1990)	10
1.6 Band structure of (a) indirect transition (b) direct transition (Shriver <i>et al.</i> , ... 12 1990)	12
1.7 Energy diagram for a dark and irradiated semiconductor (Atkins, 1995).....12	12
1.8 Energy working scheme for a redox process (Shriver <i>et al.</i> , 1990).....13	13
1.9 Illustration of the major processes occurring on a semiconductor15 particle following electronic excitation (Mills and Hunte, 1997).	15
2.1 Cross-section of the experimental set-up for the photodegradation35 process	35
2.2 Experimental set-up for the photodegradation process.....36	36
2.3 SEM-EDX JEOL JSM-6400 instrumental set-up for surface morphology43 analysis	43
2.4 XRD-6000 instrumental set-up for XRD analysis.....44	44
2.5 Perkin Elmer (model 1725X) Spectrometer FT-IR instrumental set-up45 for chemical compound substituents and functional groups analysis	45
2.6 TOC 5000A with ASI-5000A auto sampler instrumental set-up for total ...46 organic carbon analysis	46
2.7 Millipore (model 60F) Waters 600 series HPLC instrumental set-up for47 total compound existence analysis	47
3.1 A plot of mean weight of TiO ₂ versus number of times of49 dip-coating	49
3.2 Scanning electron micrograph of dried TiO ₂ prepared from sol-gel50	50
3.3 Scanning electron micrograph of TiO ₂ , distribution of titanium.....51	51
3.4 Scanning electron micrograph of TiO ₂ , distribution of oxygen.....51	51
3.5 EDX analysis spectrum of dried TiO ₂52	52
3.6 Scanning electron micrograph of TiO ₂ with 1 time of dip-coating.....53	53
3.7 Scanning electron micrograph of TiO ₂ with 2 times of dip-coating.....54	54
3.8 Scanning electron micrograph of TiO ₂ with 4 times of dip-coating.....54	54
3.9 Scanning electron micrograph of TiO ₂ with 6 times of dip-coating.....55	55
3.10 Scanning electron micrograph of TiO ₂ with 8 times of dip-coating.....55	55
3.11 EDX spectrum of TiO ₂ /Glass with 8 times of dip-coating (spectrum 1).....57	57
3.12 XRD analysis for TiO ₂ /Glass with 5 times of sol-gel dip-coating and58 calcined with different furnace temperature	58
3.13 XRD analysis for the comparison of clean glass, dried TiO ₂ powder,60 and TiO ₂ /Glass with 5 times of sol-gel dip-coating (dried at 100 °C)	60
3.14 XRD spectra for the comparison of TiO ₂ /Glass with different times (1-4)61	61



	of sol-gel dip-coating (dried at 100 °C)	
3.15	XRD pattern for the comparison of TiO ₂ /Glass with different times (4-8)62	
	of sol-gel dip-coating (dried at 100 °C)	
3.16	IR analysis for the comparison among TiO ₂ powder, crude sol-gel powder,63	
	and dried sol-gel powder	
3.17	Effect of photocatalyst and light illumination on photodegradation process65	
	of methylene blue	
3.18	Effect of photocatalyst and light illumination on photodegradation process..... 66	
	of methyl orange	
3.19	Effect of photocatalyst and light illumination on photodegradation process67	
	of indigo carmine	
3.20	Effect of photocatalyst and light illumination on photodegradation process 68	
	of chicago sky blue 6B	
3.21	Graph C/Co Vs Time, t/min for the effect of different times of sol-gel.....70	
	dip-coating (270 minutes)	
	Initial concentration (10 ppm), light intensity (4 pieces of 20 W blue	
	fluorescent lamps), 1000 mL methylene blue solution, and temperature (28 °C)	
3.22	Graph C/Co Vs Time, t/min for the effect of different times of sol-gel71	
	dip-coating (150 minutes)	
	Initial concentration (10 ppm), light intensity (4 pieces of 20 W blue	
	fluorescent lamps), 1000 mL methylene blue solution, and temperature (28 °C)	
3.23	Graph C/Co Vs Time, t/min for the effect of different initial72	
	concentration	
	5 pieces of glass with 5 times of sol-gel dip-coating repetition, light intensity	
	(4 lamps of 20 W) and temperature (28 °C)	
3.24	Graph ln C/Co Vs Time, t/min for the effect of initial concentration 75	
	5 pieces of glass with 5 times of sol-gel dip-coating repetition, light intensity	
	(4 lamps of 20 W) and temperature (28 °C)	
3.25	Graph of Total Removal of Methylene Blue/% vs Initial Concentration/ppm ...77	
3.26	Graph t/Q _t (min/ppm) Vs Time, t/min for the effect of initial80	
	concentration	
	5 pieces of glass with 5 times of sol-gel dip-coating repetition, light intensity	
	(4 lamps of 20 W) and temperature (28 °C)	
3.27	Graph C/Co Vs Time, t/min for the effect of light intensity.....81	
	5 pieces of glass, blue fluorescent lamp, 1000 mL of 10 ppm methylene	
	blue solution and temperature (28 °C)	
3.28	Graph ln C/Co Vs Time, t/min for the effect of light intensity.....82	
	5 pieces of glass, blue fluorescent lamp, 1000 mL of 10 ppm methylene	
	blue solution and temperature (28 °C).	
3.29	Graph C/Co Vs Time, t/min for the effect of different light source.....85	
	5 pieces of glass, blue fluorescent lamp, 1000 mL of 10 ppm methylene	
	blue solution and temperature (28 °C).	
3.30	Graph ln C/Co Vs Time, t/min for the effect of different light source.....86	
	5 pieces of glass, blue fluorescent lamp, 1000 mL of 10 ppm methylene	
	blue solution and temperature (28 °C).	
3.31	Graph C/Co Vs Time, t/min for the effect of different pH condition..... 90	
	5 pieces of glass, 4 blue fluorescent lamps, 1000 mL of 10 ppm methylene	
	blue solution and temperature (28 °C).	
3.32	Graph ln C/Co Vs Time, t/min for the effect of different pH condition 91	
	5 pieces of glass, 4 blue fluorescent lamps, 1000 mL of 10 ppm methylene	
	blue solution and temperature (28 °C).	
3.33	Graph C/Co Vs Time,t/min for the effect of different mass of dried TiO ₂95	

	powder	
	4 blue fluorescent lamps, 1000 mL of 10 ppm methylene blue solution and temperature (28 °C)	
3.34	Graph C/Co Vs Time, t/min for the removal efficiency comparison96 among different type of dyes	
	5 pieces of glass, 4 blue fluorescent lamps, 1000 mL of 10 ppm each dye solution, different reactive pH range for each type of dye and temperature (28 °C)	
3.35	Graph ln C/Co Vs Time, t/min for the removal rate comparison97 among different type of dyes	
	5 pieces of glass, 4 blue fluorescent lamps, 1000 mL of 10 ppm each dye solution, different reactive pH range for each type of dye and temperature (28 °C)	
3.36	Total intermediates produced in the photodegradation process of methylene... 101 blue	
3.37	Intermediates produced in the photodegradation process of methylene 102 blue at time, t/min	
3.38	Total intermediates produced in the photodegradation process of methyl104 orange	
3.39	Intermediates produced in the photodegradation process of methyl orange 104 at time, t/min	
3.40	Fragmentation scheme in MS ² , MS ³ of methyl orange molecule (Balocchi106 <i>et al.</i> , 2002)	
3.41	Fragmentation scheme of methyl orange degradation products, A107 (Balocchi <i>et al.</i> , 2002)	
3.42	Fragmentation scheme of methyl orange degradation products, B108 (Balocchi <i>et al.</i> , 2002)	
3.43	Total intermediates produced in the photodegradation process of chicago110 sky blue 6B	
3.44	Intermediates produced in the photodegradation process of chicago sky111 blue 6B at time, t/min.	
3.45	Total intermediates produced in the photodegradation process of indigo112 carmine	
3.46	Intermediates produced in the photodegradation process of indigo 113 carmine at time, t/min.	
3.47	Total intermediates produced in the photodegradation process of mixed115 dyes	
3.48	Intermediates produced in the photodegradation process of mixed dyes116 at time, t/min (up to 150 minutes)	
3.49	Intermediates produced in the photodegradation process of mixed dyes117 at time, t/min (up to 270 minutes)	
3.50	Total organic carbon removed in the photodegradation process for119 various organic waste water solution.	
3.51	HPLC chromatogram for methylene blue 120	
3.52	HPLC chromatogram for methyl orange 121	
3.53	HPLC chromatogram for indigo carmine 122	
3.54	HPLC chromatogram for chicago sky blue 6B123	
3.55	HPLC chromatogram for mixed dyes (10 ppm)124	
3.56	HPLC chromatogram for mixed dyes (2.5 ppm) 125	
3.57	HPLC chromatogram for waste water solution.....127	

LIST OF ABBREVIATIONS

MB	methylene blue
MO	methyl orange
IC	indigo carmine
CSB	chicago sky blue 6B
VB	valence band
CB	conduction band
SEM	scanning electron microscope
EDX	energy dispersive X-ray spectrometer
TiO₂/Glass	titanium dioxide coated on glass
XRD	X-ray diffractometer or X-ray diffraction photometer
FT-IR	Fourier Transform-Infra Red
MO	molecular orbital
AO	atomic orbital
Mw	molecular weight



CHAPTER 1

INTRODUCTION

Potable water is a must for our life. The water that we use must be safe and free from apparent turbidity, colour, odour or any objectionable taste. However, there is a rising concern nowadays for the continuous supply of potable water due to the pollution of the water source arising as inevitable byproducts from industrial processes, agricultural treatment of crops and accidental spills or leaks from containers. One of the main pollution source of wastewater comes from the dyeing and finishing processes.

The textile industry consumes considerable amounts of water during the dyeing and finishing operations. Dyes are extensively used, hence wastewaters discharged in rivers or public sewage treatment plants are highly contaminated. Dyes are highly coloured organic substances. Thus, the presence of very small amounts of dyes in water will affect the aesthetic nature of water. Besides, the polluted wastewater is sometimes found to be carcinogenic and mutagenic. However, colour substances in dyeing effluents normally cause certain difficulties in traditional biological treatment processes due to their nonbiodegradable nature. Thus, it is necessary to remove colour from dyeing effluents with the help of some physical or chemical treatment processes (Li and Zhang, 1996 and Baker *et al.*, 2000).

Over the past decade, various methods have been developed to remove contaminant in wastewater. Biodegradable organic substances can be removed using biological treatment. Chemical means of removing contaminant in wastewater involve the addition of chemicals or by other specific chemical reactions, while the physical

ways of wastewater contaminant removal consist of screening, mixing, filtration, gas transfer, floatation, sedimentation, and flocculation.

Presently, photocatalytic mineralisation of pollutants, especially organic pollutants had gained much attention. Photocatalysis is the acceleration of a photoreaction by the presence of a catalyst (Mills and Hunte, 1997). It involved the heterogeneous photocatalytic degradation of pollutants using semiconductors. In this regard, much attention has been focused on titanium dioxide (TiO_2) particles since this semiconductor is stable with respect to anodic dissolution (Zang *et al.*, 1995). It is non-toxic, insoluble, comparatively cheap, is available in some forms having high photoactivity and it can be activated by sunlight.

Investigation of the photochemical processes taking place in titanium dioxide/organic dyes systems is of considerable practical interest not only for the development of the processes involved in the purification of industrial effluents but also because the adsorbed dyes can sensitize photocatalysts and semiconducting materials based on titanium dioxide to light in the near UV and visible regions (Khalyavka *et al.*, 2001).

It has been found that titanium dioxide illuminated with light energy greater than bandgap energy ($\lambda < 380 \text{ nm}$) can act as photocatalyst to mineralize toxic and bioresistant organic compounds from aqueous solution to non-toxic and safer compounds, namely mineral acids, carbon dioxide and water before it is released into the environment. Specifically, it should also be effective to photomineralize commercial dyes such as methylene blue, methyl orange, and indigo carmine to mineral acids, carbon dioxide and water.

Titanium dioxide was supported on glass to avoid filtration and resuspension problem associated with the use of catalyst suspension before the water was discharged into the environment. Furthermore, the removal rate of the pollutants can also be enhanced by anchoring titanium dioxide on supports including zeolite (Xu and Langford, 1995), sand (Matthews, 1991), silica and activated carbon (Torimoto *et al.*, 1996) and glass matrix (Al-Ekabi and Serpone, 1988).

1.1 Theory of Semiconductor

Generally, a semiconductor can be defined as a substance having electrical conductivity between metals and insulators. Metal is a good electric and heat conductor, while semiconductor has a lower conductivity than that typical of metals. However, the magnitude of the conductivity is not the criterion of the distinction.

The electronic conduction in a solid can be explained with the help of Molecular Orbital (MO) Theory. We can define two kinds of electrons in a semiconductor; bonded and unbonded or free electrons. The electrons in a semiconductor will be distributed among the same number of MO formed as a linear combination of atomic orbital (LCAO).

In a semiconductor such as TiO_2 , free electron energies are quantised in a large number of closely spaced energy levels and formed the conduction band (CB). The covalence bonds' electrons of a semiconductor also have a range of permitted energies.

These levels are also closely spaced and form an energy band called the valence band (VB). There is a gap between these two bands where there are no orbitals. The band gap acts as a barrier to electronic mobility. The energy levels of the CB is located above the energy levels of the VB.

Electrons are freed when they acquire enough energy and leave behind them gaps in the bonds, called holes (h^+). Band gap energy (E_g) is the absolute minimum energy required to promote electrons from the highest level of VB to the lowest level of CB. This can be represented in the energy levels diagram by a gap between VB and CB (Figure 1.1).

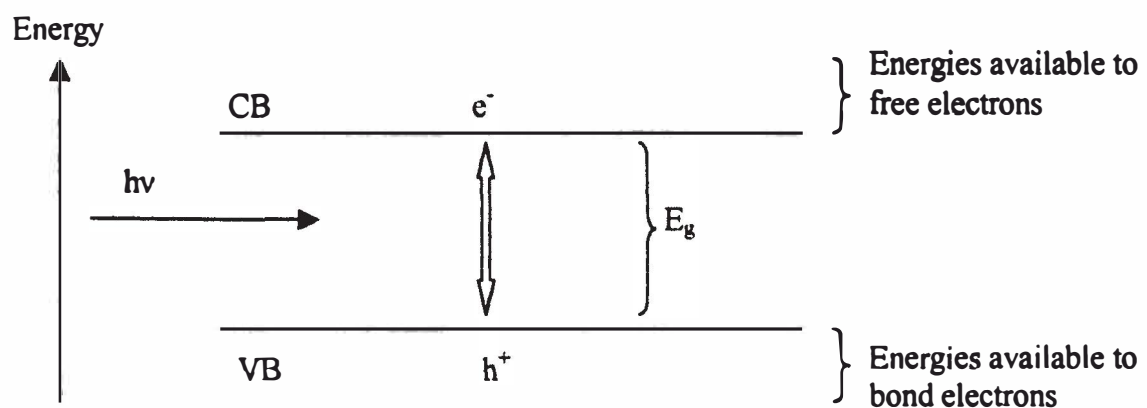


Figure 1.1: The energy diagram for a semiconductor, showing the band gap energy (Nogueira and Wilson, 1993).

The block arrow in Figure 1.1 represents the transition of an electron from VB to CB. Absorption by the particle of photons with energy ($h\nu$) greater than the bandgap causes photoexcitation of electron-hole pairs. The band gap energy for TiO_2 is 3.32 eV (Nogueira and Wilson, 1993).

As indicated in Figure 1.2, for many compounds, as the number of monomeric units, N , in a particle increases, the energy necessary to photoexcite the particle decreases. In the limit when $N \geq 2000$, it is possible to end up with a particle which exhibits the band electronic structure of a semiconductor (Mills and Hunte, 1997). As illustrated in Fig. 1.2, in which the highest occupied band (HOMO, the valence band) and lowest unoccupied energy band (LUMO, the conduction band) are separated by a bandgap E_g , a region devoid of energy levels in a perfect crystal.

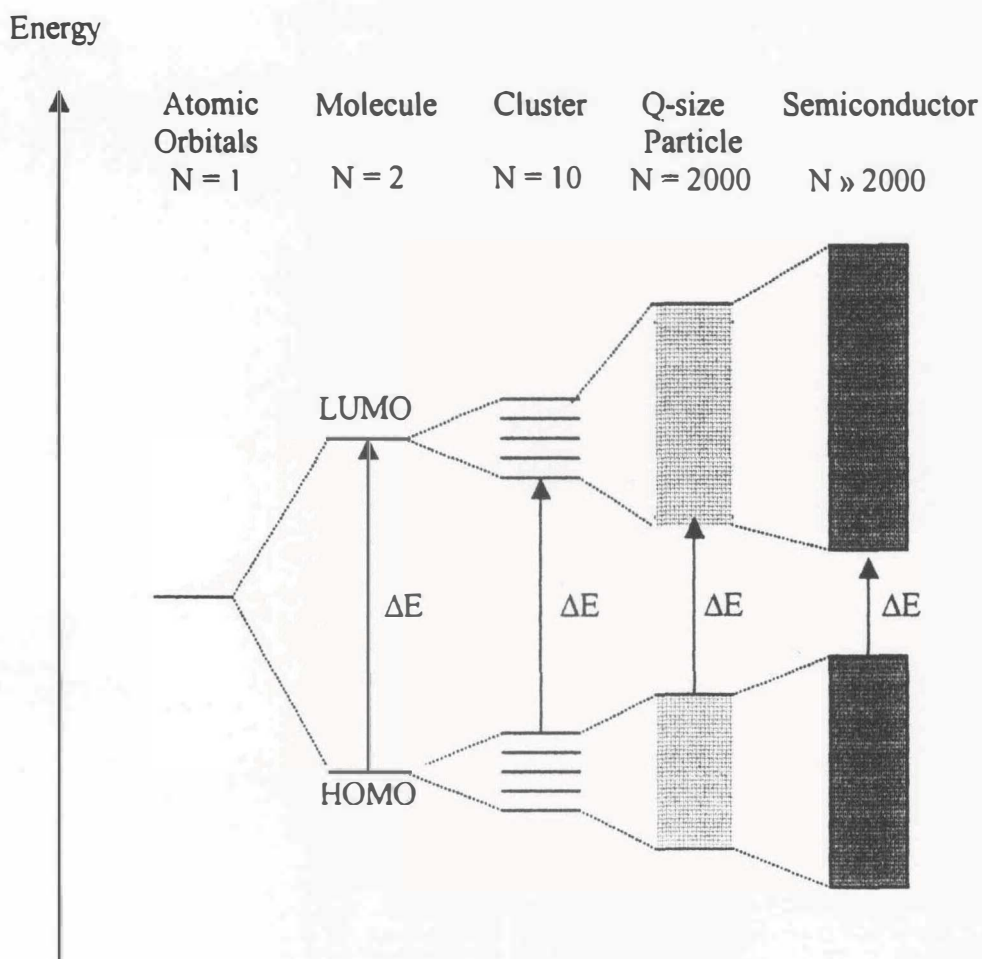


Figure 1.2: Change in the electronic structure of a semiconductor compound as the number N of monomeric units present increase from unity to clusters of more than 2000 (Mills and Hunte, 1997)